

2810 Clark Avenue • St. Louis, MO 63103-2574 • (314) 531-8080 • FAX (314) 531-8085
 Chemical, Metallurgical, Mechanical, Nondestructive, Environmental Testing, Analyses and Field Service.

ARCOPLAST
 1873 Williamstown Drive
 St. Peters, MO 63376

May 21, 2020
 Lab No. 20P-2156
 Invoice No. 270963
 Page 16 of 26

Attention: Ghislain Beauregard


REPORT OF MECHANICAL TEST

Group 8:

Arcoplast GFRMC Panel 9.5mm

SUBJECT: Tensile Strength Test
METHOD: ASTM D638-14
INSTRUMENT: Instron 5500R with Bluehill software
RESULTS:

Specimen #	Area (in ²)	Max Load (lbf)	Tensile Strength (psi)	Modulus (psi)
1	0.287	1269	4420	25749.8
2	0.291	1240	4270	25017.8
3	0.281	1266	4510	24768.3
4	0.291	1136	3900	21941.7
5	0.289	1027	3560	23840.0
Average		1188	4130	24263.5

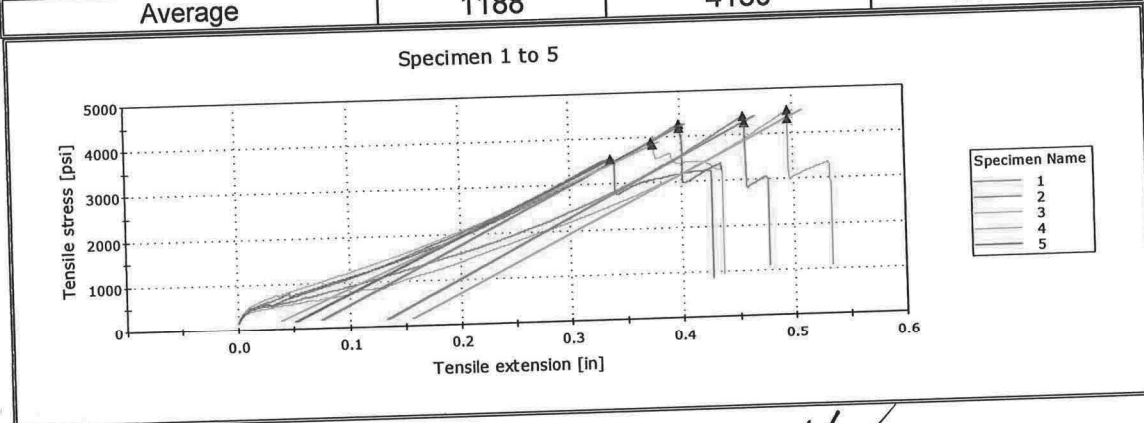


 Karl Schmitz, Director
 Materials Testing

KS/jlb